



Longitudinal and circumferential mechanical behavior of human cerebral artery

Dominique Ambard, Omer Eker, Simon Le Floc'h, Vincent Costalat, Mathieu Sanchez, Franck Jourdan

► **To cite this version:**

Dominique Ambard, Omer Eker, Simon Le Floc'h, Vincent Costalat, Mathieu Sanchez, et al.. Longitudinal and circumferential mechanical behavior of human cerebral artery. 21st congress of the european society of biomechanics, Jul 2015, Prague, Czech Republic. 21st congress of the european society of biomechanics. <hal-01219454>

HAL Id: hal-01219454

<https://hal.archives-ouvertes.fr/hal-01219454>

Submitted on 22 Oct 2015

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

LONGITUDINAL AND CIRCUMFERENTIAL MECHANICAL BEHAVIOR OF HUMAN CEREBRAL ARTERY

Ambard D.¹, Eker O.F.², Le Floch S.¹, Costalat V.², Sanchez M.¹, Jourdan F.¹

¹ LMGC, UMR 5508 – University of Montpellier, France, dominique.ambard@um2.fr

² Service de Neuroradiologie, Hôpital Gui de Chauliac, CHRU Montpellier, France

Introduction

The prevalence of unruptured intracranial aneurysms in the general population, as reported by a recent review [Wardlaw, 2000], ranges between 3% and 6.6%. However, the incidence of ruptured aneurysms is low, with approximately 0.5% per year, suggesting that very few aneurysms rupture. Clearly, new patient-specific indexes predicting aneurysm risk of rupture should be proposed, in order to guide therapeutic decision for unruptured aneurysm.

Previously, we showed that aneurysmal pulsatility might be a relevant patient-specific predictor of aneurysm risk of rupture [Sanchez, 2013], as the pulsatility showed to provide information on the degradation of the mechanical properties of ruptured aneurysm tissue. However, the biomechanical properties of healthy arteries of circle of Willis are poorly reported. In this study, we attempted to identify the biomechanical behavior of healthy intracranial artery taken from autopsied subjects.

Materials and methods

Five circle of Willis were taken from 5 autopsied subjects who died from an extracranial cause. Their ages ranges from 30 to 80 years. This research study protocol was approved by the local ethic committee. From all circle of Willis, 16 segment of artery was used in this study.

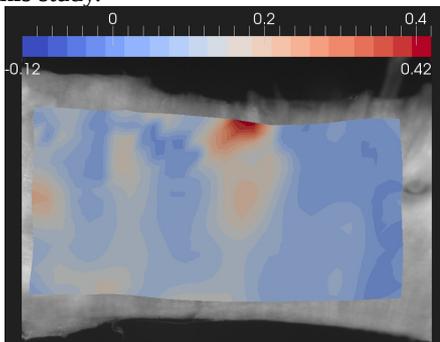


Figure 1: Green Lagrange strain from DIC.

Under microscopy, the aneurysmal wall samples were dissected in a longitudinal direction and circumferential direction to obtain two regular rectangular pieces (Fig.1). A uniaxial stretch test was carried out on the sample within the warmed (40°C) physiological liquid in order to simulate the in vivo

conditions. This testing device was composed of a Texture Analyzer with a 50 N load cell and two digital video camera to compute a DIC analysis (Fig.1).

To obtain the strain/stress relation, we proceed to a mathematical matching to determine the corresponding hyperelastic model and its coefficients. In our cases, the best match was obtained with a 2 parameters Yeoh model (eq. 1) :

$$W(I_1) = C_1(I_1 - 3) + C_2(I_1 - 3)^2 \quad (1)$$

Results and discussion

The mechanical behaviors in the longitudinal and circumferential directions are significantly different (Tab. 1) for healthy arteries, indicating a fibrous, structured soft tissue. Indeed, the mechanical behavior is stiffer in the longitudinal direction than in the circumferential direction, in agreement with other studies [Hu, 2007].

We also compared the mean stiffness's of the healthy arteries to the stiffness's of the aneurysmal tissue. We found a significant difference ($p=0.01$), with a mean reduction factor of 2.8 on parameter C_2 between healthy artery and aneurysmal tissue, suggesting a more linear behavior in the aneurysmal tissue.

Table 1: C_1 and C_2 coefficients from human cerebral artery with interval confidence (95%).

Direction	C_1 [Mpa]	C_2 [Mpa]
Longitudinal	0.2 ± 0.11	12.3 ± 7.35
Circumferential	0.1 ± 0.06	4.4 ± 3.21
p value	0.1152	0.0365 *

Conclusion

Variations of the biomechanical properties was found between aneurysmal tissue and healthy artery tissue. First, a significant reduction of the stiffness was found, in particular concerning the C_2 parameter in the Yeoh model used between healthy and degraded tissue, suggesting that the aneurysm has a more linear behavior than healthy tissue. Second, the mechanical behavior of degraded tissue is close to the mechanical behavior of circumferential direction of healthy arteries.

References

- Wardlaw *et al*, Brain, 123:205-221, 2000
- Sanchez *et al*, Ann. Biomed. Eng., 41:28-40, 2013
- Hu *et al*, J. Biomechanics, 40:2559-2563, 2007